

A Triplet Resonance in Superconducting $\text{FeSe}_{0.4}\text{Te}_{0.6}$

Wei Bao,^{1,*} A. T. Savici,² G. E. Granroth,³ C. Broholm,² K. Habicht,⁴ Y. Qiu,^{5,6} Jin Hu,⁷ Tijiang Liu,⁷ and Z.Q. Mao⁷

¹*Department of Physics, Renmin University of China, Beijing 100872, China*

²*Institute for Quantum Matter and Department of Physics and Astronomy,
The Johns Hopkins University, Baltimore, Maryland 21218, USA*

³*Neutron Scattering Sciences Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA*

⁴*Helmholtz-Zentrum Berlin für Materialien und Energy, D-14109 Berlin, Germany*

⁵*NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, MD 20899, USA*

⁶*Department of Materials Science and Engineering,
University of Maryland, College Park, MD 20742, USA*

⁷*Department of Physics and Engineering Physics,
Tulane University, New Orleans, Louisiana 70118, USA*

(Dated: February 8, 2010)

From heavy fermions to cuprates and iron pnictides, a spin resonance at $\hbar\Omega_0 \propto k_B T_c$ is a staple of nearly magnetic superconductors. Possible explanations include a two-particle bound state or loss of magnon damping in the superconductor. While both scenarios suggest a central role for magnetic fluctuations, distinguishing them is important to identify the right theoretical framework and to guide the search for higher temperature superconductors. Using inelastic neutron scattering technique, we show that the spin resonance in optimally doped $\text{FeSe}_{0.4}\text{Te}_{0.6}$ splits into three peaks in a high magnetic field, a signature of a two-particle triplet bound state.

PACS numbers: 74.70.-b, 78.70.Nx, 74.20.Mn, 74.25.Ha

Initially discovered in cuprates[1–5], then heavy fermion systems[6–9], and now iron pnictide/chalcogenide superconductors[10–12], a spin resonance is arguably the most prominent experimental feature of unconventional superconductors[13]. The leading interpretation is a triplet bound state formed by two Bogoliubov-de Gennes quasiparticles in the superconducting state. The resonance intensity is enhanced by the coherence factor of a momentum-space modulated superconducting order parameter[14–19]. A different class of theories associates the resonance with a remnant magnon of the parent antiferromagnetic state[20, 21] - the enhancement below T_c is attributed to loss of the particle-hole damping channel within the superconducting gap. While each interpretation may have merit in different materials, we report an experimental result that makes a clear distinction for optimally doped $\text{FeSe}_{0.4}\text{Te}_{0.6}$ superconductor. By splitting the resonance into three modes in a high magnetic field, we show it is associated with a spin triplet, thus pointing decidedly to a two-particle bound state. In contrast, a conventional magnon is generally a doublet that may split into two modes in a field[22].

The Fe_{1+y}Se superconductor[23] contains the same electronically active iron-chalcogen or pnictogen layers as in other families of the iron-based superconductors[24–26]. The superconducting transition temperature T_c can be raised from 8 K to 14.6 K through partial substitution of Se by Te, while the superconducting volume fraction can be enhanced and the transition sharpened by tuning the iron/chalcogen ratio close to one ($y \approx 0.03$)[27]. A fortuitous aspect of the $\text{Fe}(\text{Se},\text{Te})$ superconductors is the

availability of large high-quality single crystalline samples, which allowed us to unambiguously observe the development of a spin resonance above a gap in the superconducting state of $\text{FeSe}_{0.4}\text{Te}_{0.6}$ in inelastic neutron scattering experiments[12]. As in optimally doped $\text{BaFe}_{1.84}\text{Co}_{0.16}\text{As}_2$ ($T_c = 22$ K) [11], the resonance disperses only with in-plane momenta, indicating a quasi-two-dimensional superconducting state.

An optimized set of $\text{FeSe}_{0.4}\text{Te}_{0.6}$ single crystals with narrower mosaic and higher $T_c = 14.6$ K than those used previously[12] was prepared for the experiment. The magnetic field was applied along the c -axis of the tetragonal $P4/nmm$ unit cell[28] and thus perpendicular to the Fe square plane. Fig. 1 shows constant $\mathbf{Q}=(\frac{1}{2}, \frac{1}{2}, 0)$ scans at a temperature $T = 1.7$ K. The upturn at high energies is background associated with low scattering angles where the direct beam impinges on the detection system. In zero magnetic field, the resonance is centered at $\hbar\Omega_0 = 7.1(1)$ meV, yielding a ratio $\hbar\Omega_0/k_B T_c \approx 5.6$ comparable to the previously reported value for $\text{Fe}(\text{Se},\text{Te})$ [12] and cuprates $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ [1], $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ [3] and $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+x}$ [4], but larger than 4.3-4.5 for doped BaFe_2As_2 [10, 11] and 2-4 for $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ [5] and heavy fermion superconductors[6–9]. In a 14 T magnetic field, the peak broadens and fine structure appears. In particular there are two clearly defined maxima at 5 meV and 7 meV. Field dependence beyond 8.5 meV is less than the statistical accuracy in this background dominated part of the spectrum.

To clearly extract the magnetic signal, especially at higher energies, we measured a background spectrum at a wave vector transfer $\mathbf{Q}=(0.68, 0.18, 0)$ where magnetic

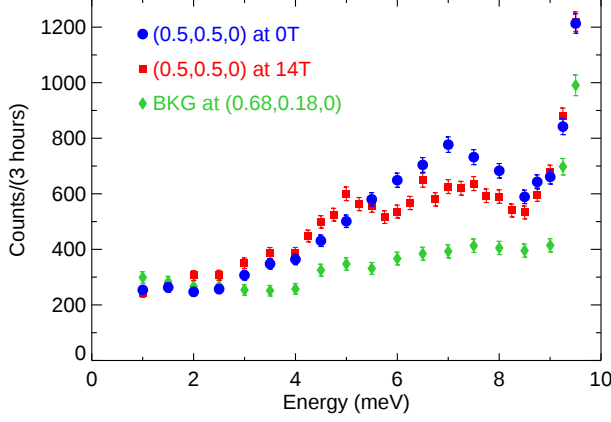


FIG. 1: Low temperature (1.7 K) inelastic neutron scattering data from $\text{FeSe}_{0.4}\text{Te}_{0.6}$ in the superconducting state. Blue circles are zero field data, while red squares were acquired in a field of 14 Tesla. Green diamonds represent the background, acquired with the sample rotated 30 degrees from $(0.5,0.5,0)$, corresponding to $(0.68,0.18,0)$. The upturn at high energies in all data sets is associated with the low scattering angle limit of the spectrometer where the incident beam impinges on the detection system.

scattering is negligible[12]. The background subtracted data were normalized to represent a differential scattering cross section by comparing to energy integrated acoustic phonon data and are shown in Fig. 2. The integrated magnetic scattering intensity is conserved to within error, consistent with an accurate measurement of field effects from a relatively weak perturbation at low temperatures. A spectrum that is symmetric about the central peak and consists of three lorentzians was fitted to the data and is shown as solid lined in Fig. 2. The zero field peak is considerably broader than the three high field peaks. This suggests the zero field resonance encompasses overlapping anisotropy shifted components that resolve in a field. In fitting to lower field data, we forced equal peak widths, intensity, and symmetric splitting around the central peak, as indicated by the 14 T data. The inset to Fig. 2 shows the fitted positions of spectral maxima versus field thus extracted from constant $\mathbf{Q}$ scans at several fields. To within error, the central peak position is independent of field while the upper and lower peak positions can be described by the following expression: $\hbar\omega = \hbar\Omega_0 \pm \sqrt{\delta^2 + (g\mu_B B)^2}$ where $g = 2.5(4)$ and anisotropy $\delta = 1.2(4)$ meV.

The observation of three peaks in a field is consistent with transitions between a singlet ground state and a triplet excited state that is field split by the Zeeman term. Such a level scheme can result from a near spin-space isotropic attraction between identical quasiparticles that carry spin.[14–19]. High field extrapolation of the peaks in the inset to Fig. 2 yields an esti-

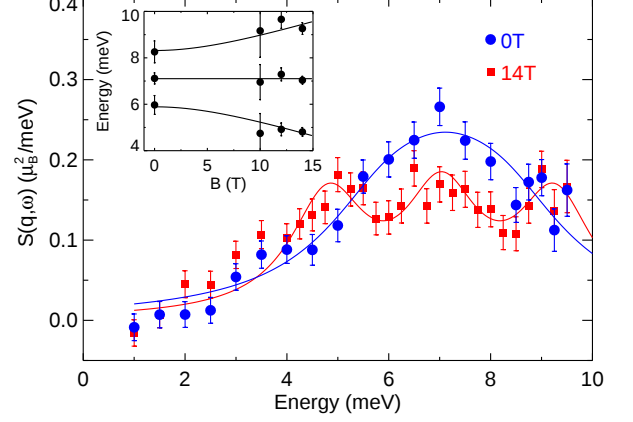


FIG. 2: Background subtracted low temperature inelastic scattering data from $\text{FeSe}_{0.4}\text{Te}_{0.6}$ at zero field (blue circles) and 14 Tesla (red squares). Lines through the data indicate fits to three lorentzians constrained to have an equal width. In fitting data at fields below 14 Tesla, we further constrained the peaks to have equal spectral weight, which is the case at 14 Tesla. The inset shows the field dependence of peak positions extracted from such fits. The solid lines through these data correspond to the fit described in the text.

mate for the critical field at which the lower member of the triplet becomes degenerate with the ground state: $\mu_0 H_c = \sqrt{(\hbar\Omega_0)^2 - \delta^2} / g\mu_B = 47(9)$ T. The match of this value and the upper critical field of $\mu_0 H_{c2} \approx 47$ T inferred from high field resistivity data[29] indicates the intimate connection between the formation of coherent singlet-triplet spectrum and superconductivity in $\text{FeSe}_{0.4}\text{Te}_{0.6}$.

We shall now address some important quantitative aspects of the high field data. With the field direction and c -axis as the quantization axis, the central field-independent transition must be between states with the same projection of dipole moment along the field ($\delta m = 0$) and so the finite transition matrix element is that of the $\hat{S}_z$ operator. Conversely $\delta m = \pm 1$ for the field dependent modes, which therefore are associated with the $\hat{S}_x$ and $\hat{S}_y$ operators. Unpolarized magnetic neutron scattering probes $\mathcal{I}_m(\mathbf{q}, \omega) = \mathcal{S}^{zz} + (1 - \hat{q}_x^2)\mathcal{S}^{xx} + (1 - \hat{q}_y^2)\mathcal{S}^{yy}$. Four fold symmetry implies $\mathcal{S}^{xx} = \mathcal{S}^{yy} \equiv \mathcal{S}^\perp$ so that $\mathcal{I}_m(\mathbf{q}, \omega) = \mathcal{S}^{zz} + \mathcal{S}^\perp$. For a weakly field perturbed isotropic system where $\mathcal{S}^{zz}$ and $\mathcal{S}^\perp$ carry equal spectral weight, the field independent longitudinal component (the central peak) and the field dependent transverse component (the sum of the upper and lower peaks) should carry equal spectral weight. This is consistently observed for field split singlet-triplet transitions associated with exchange coupled atomic spin degrees of freedom in a variety of insulating quantum magnets[30]. In contrast for the resonance in $\text{FeSe}_{0.4}\text{Te}_{0.6}$, the total intensity associated with the total field dependent modes is approximately twice the intensity of the field indepen-

dent mode. This indicates a factor two enhancement of the transverse spectral density that surely is an important characteristic of the superconducting state.

The relation between the resonance and superconducting pair correlations is a hotly debated theoretic issue[31–35]. A useful diagnostic from inelastic magnetic neutron scattering is the change in the first moment across the superconducting phase transition:

$$\Delta \langle E(\mathbf{q}) \rangle = \left(\frac{\hbar}{2\mu_B} \right)^2 \int_0^\infty \omega \text{Tr} \{ \Delta \mathcal{S}(\mathbf{q}, \omega) (1 - e^{-\beta \hbar \omega}) \} d\omega. \quad (1)$$

For spin exchange models of magnetism, $\Delta \langle E(\mathbf{q}) \rangle = -\frac{1}{3} \sum_{\mathbf{d}} J_{\mathbf{d}} \langle \mathbf{S}_0 \cdot \mathbf{S}_{\mathbf{d}} \rangle (1 - \cos \mathbf{q} \cdot \mathbf{d})$. For an itinerant magnetic system such as $\text{FeSe}_{0.4}\text{Te}_{0.6}$, we expect the amplitude of $\Delta \langle E(\mathbf{q}) \rangle$ to monitor magnetic exchange energy through the superconducting phase transition. Assuming $\Delta \mathcal{S} = \mathcal{S}(1.7\text{K}) - \mathcal{S}(30\text{K})$ vanishes beyond a cut-off $\hbar\omega_c = 13$ meV, as suggested by measurements in previous study[12], $\Delta \langle E(\mathbf{q}) \rangle$ relative to 30 K was calculated from the normalized difference data to be 1.7(6) meV per Fe atom. For comparison the net condensation energy has been estimated to be 1.1 J/mole ≈ 0.01 meV/Fe based on specific heat measurements[27]. A similar orders of magnitude difference between $\Delta \langle E(\mathbf{q}) \rangle$ and the net thermodynamic condensation energy was previously noted in the heavy fermion superconductor CeCoIn_5 [9]. The implication is that superconductivity is driven by the reduced magnetic exchange energy that it entails. The small net condensation energy indicates an almost equal increase in the electronic kinetic energy in the superconducting state.

We have presented evidence of field induced fine structure in the spin resonance of a magnetic superconductor. Three peaks emerge from a broad zero field maximum reminiscent of Zeeman splitting of a triplet bound-state formed by two identical Bogoliubov-de Gennes quasiparticles with weakly anisotropic attraction. Quantitative analysis shows the shift in the magnetic exchange energy associated with the triplet exceeds the net condensation energy by two orders of magnitude, and the inferred critical field where the Zeeman energy exceeds the bound state energy matches the upper critical field. The high field neutron data show that magnetic fluctuations play a central role in iron superconductivity and suggest that the formation of a triplet bound state actually drives superconductivity in $\text{FeSe}_{0.4}\text{Te}_{0.6}$.

Work at Tulane was supported by the NSF under grant DMR-0645305 (for materials) and the DOE under DE-FG02-07ER46358 (for graduate students). Work at JHU/IQM was supported by the DOE under DE-FG02-08ER46544. Work at ORNL is through UT-Battelle, LLC, under Contract No. DE-AC05-00OR22725 with the USDOE.

METHODS

Single crystals of $\text{FeSe}_{0.4}\text{Te}_{0.6}$ were grown by a flux method. Three crystals, weighing 7.9, 3.8 and 3.6 g respectively, were mutually aligned so that the reciprocal $(h, k, 0)$ plane corresponds to the horizontal scattering plane of the V2 FLEX cold neutron triple-axis spectrometer at HZB. Neutron scattering measurements were conducted using the fixed $E_f = 5$ meV configuration with a cold Be filter placed after the sample and pyrolytic graphite for both monochromator and analyzer. The lattice parameters of the tetragonal $P4/nmm$ unit cell are $a = b = 3.802$ and $c = 6.061 \text{ \AA}$ at room temperature. The mosaic full width at half maximum of the individual samples ranges from 1.2 to 1.6 degrees, and the co-aligned assembly mosaic was 2.2 degrees. The sample temperature and applied magnetic field were established by a 15 T vertical-field cryomagnet.

* Electronic address: wbao@ruc.edu.cn

- [1] J. Rossat-Mignod, L. Regnault, C. Vettier, P. Bourges, P. Burlet, J. Bossy, J. Henry, and G. Lapertot, *Physica C* **185-189**, 86 (1991).
- [2] H. A. Mook, M. Yethiraj, G. Aeppli, T. Mason, and T. Armstrong, *Phys. Rev. Lett.* **70**, 3490 (1993).
- [3] H. F. Fong, P. Bourges, Y. Sidis, L. P. Regnault, A. Ivanov, G. D. Gu, N. Koshizuka, and B. Keimer, *Nature* **398**, 588 (1999).
- [4] H. F. He, P. Bourges, Y. Sidis, C. Ulrich, L. P. Regnault, S. Pailh s, N. S. Berzigiarova, N. N. Kolesnikov, and B. Keimer, *Science* **295**, 1045 (2002).
- [5] J. M. Tranquada, C. H. Lee, K. Yamada, Y. S. Lee, L. P. Regnault, and H. M. R nnow, *Phys. Rev. B* **69**, 174507 (2004).
- [6] N. Metoki, Y. Haga, Y. Koike, and Y. Onuki, *Phys. Rev. Lett.* **80**, 5417 (1998).
- [7] N. K. Sato, N. Aso, K. Miyake, R. Shiina, P. Thalmeier, G. Varelogiannis, C. Geibel, F. Steglich, P. Fulde, and T. Komatsubara, *Nature* **410**, 340 (2001).
- [8] O. Stockert, J. Arndt, A. Schneidewind, H. Schneider, H. Jeevan, C. Geibel, F. Steglich, and M. Loewenhaupt, *Physica B* **403**, 973 (2008).
- [9] C. Stock, C. Broholm, J. Hudis, H. J. Kang, and C. Petrovic, *Phys. Rev. Lett.* **100**, 087001 (2008).
- [10] A. D. Christianson, E. A. Goremychkin, R. Osborn, S. Rosenkranz, M. D. Lumsden, C. D. Malliakas, I. S. Todorov, H. Claus, D. Y. Chung, M. G. Kanatzidis, et al., *Nature* **456**, 930 (2008).
- [11] M. D. Lumsden, A. D. Christianson, D. Parshall, M. B. Stone, S. E. Nagler, G. MacDougall, H. A. Mook, K. Lokshin, T. Egami, D. L. Abernathy, et al., *Phys. Rev. Lett.* **102**, 107005 (2009).
- [12] Y. Qiu, W. Bao, Y. Zhao, C. Broholm, V. Stanev, Z. Tesanovic, Y. C. Gasparovic, S. Chang, J. Hu, B. Qian, et al., *Phys. Rev. Lett.* **103**, 067008 (2009).
- [13] Y. J. Uemura, *Nature Mater.* **8**, 253 (2009).
- [14] K. Maki and H. Won, *Phys. Rev. Lett.* **72**, 1758 (1994).
- [15] P. Monthoux and D. J. Scalapino, *Phys. Rev. Lett.* **72**,

- 1874 (1994).
- [16] E. Demler and S.-C. Zhang, Phys. Rev. Lett. **75**, 4126 (1995).
 - [17] I. Eremin, G. Zwicknagl, P. Thalmeier, and P. Fulde, Phys. Rev. Lett. **101**, 187001 (2008).
 - [18] I. I. Mazin, D. J. Singh, M. D. Johannes, and M. H. Du, Phys. Rev. Lett. **101**, 057003 (2008).
 - [19] M. M. Korshunov and I. Eremin, Phys. Rev. B **78**, 140509(R) (2008).
 - [20] D. K. Morr and D. Pines, Phys. Rev. Lett. **81**, 1086 (1998).
 - [21] C. D. Batista, G. Ortiz, and A. V. Balatsky, Phys. Rev. B **64**, 174507 (2001).
 - [22] J. V. Kranendonk and J. H. V. Vleck, Rev. Mod. Phys. **30**, 1 (1958).
 - [23] F.-C. Hsu, J.-Y. Luo, K.-W. Yeh, T.-K. Chen, T.-W. Huang, P. M. Wu, Y.-C. Lee, Y.-L. Huang, Y.-Y. Chu, D.-C. Yan, et al., PNAS **105**, 14262 (2008).
 - [24] Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, J. Am. Chem. Soc. **130**, 3296 (2008).
 - [25] M. Rotter, M. Tegel, and D. Johrendt, Phys. Rev. Lett. **101**, 107006 (2008).
 - [26] X. Wang, Q. Liu, Y. Lv, W. Gao, L.X. Yang, R. Yu, F. Li, and C. Jin, Solid State Comm. **148**, 538 (2008).
 - [27] T. Liu, X. Ke, B. Qian, J. Hu, D. Fobes, E. K. Vehstedt, H. Pham, J. Yang, M. Fang, L. Spinu, et al., Phys. Rev. B **80**, 174509 (2009).
 - [28] W. Bao, Y. Qiu, Q. Huang, M. A. Green, P. Zajdel, M. R. Fitzsimmons, M. Zhernenkov, S. Chang, M. Fang, B. Qian, et al., Phys. Rev. Lett. **102**, 247001 (2009).
 - [29] M. H. Fang, J. H. Yang, F. F. Balakirev, Y. Kohama, J. Singleton, B. Qian, Z. Q. Mao, H. D. Wang, and H. Q. Yuan, arXiv:0909.5328 (2009).
 - [30] C. Broholm, G. Aeppli, Y. Chen, D. C. Dender, M. Enderle, P. R. Hammar, Z. Honda, K. Katsumata, C. P. Landee, M. Oshikawa, et al., in *High Magnetic Fields - applications in condensed matter physics and spectroscopy*, edited by C. Berthier, L. P. Lévy, and G. Martinez (Springer-Verlag, 2002), pp. 211–234.
 - [31] E. Demler and S.-C. Zhang, Nature **396**, 733 (1998).
 - [32] P. Dai, H. A. Mook, S. M. Hayden, G. Aeppli, T. G. Perring, R. D. Hunt, and F. D. an, Science **284**, 1344 (1999).
 - [33] H.-Y. Kee, S. A. Kivelson, and G. Aeppli, Phys. Rev. Lett. **88**, 257002 (2002).
 - [34] A. Abanov, A. Chubukov, M. Eschrig, M. R. Norman, and J. Schmalian, Phys. Rev. Lett. **89**, 177002 (2002).
 - [35] W.-C. Lee and A. H. MacDonald, Phys. Rev. B **78**, 174506 (2008).